

UNCLASSIFIED

SECURITY CLASSIFICATION OF THIS PAGE

| REPORT DOCUMENTATION PAGE  |       |  |  | Form Approved<br>OMB No. 0704-0188                 |                                |
|--|-------|--|--|--|--------------------------------|
| 1a. REPORT SECURITY CLASSIFICATION<br>Unclassified   |       |  | 1b. RESTRICTIVE MARKINGS<br>None   |  |                                |
| 2a. SECURITY CLASSIFICATION AUTHORITY<br>N/A   |       |  | 3. DISTRIBUTION/AVAILABILITY OF REPORT<br><br>Approved for public release; distribution unlimited. |  |                                |
| 2b. DECLASSIFICATION/DOWNGRADING SCHEDULE<br>N/A   |       |  |  |  |                                |
| 4. PERFORMING ORGANIZATION REPORT NUMBER(S)<br>Report No. 2496   |       |  | 5. MONITORING ORGANIZATION REPORT NUMBER(S)<br>N/A   |  |                                |
| 6a. NAME OF PERFORMING ORGANIZATION<br>US Army Belvoir RD&E Center<br>Materials, Fuels and Lubricants Dir.   |       | 6b. OFFICE SYMBOL<br>(If applicable)<br>STRBE-VU | 7a. NAME OF MONITORING ORGANIZATION<br>N/A   |  |                                |
| 6c. ADDRESS (City, State, and ZIP Code)<br><br>Fort Belvoir, VA 22060-5606   |       |  | 7b. ADDRESS (City, State, and ZIP Code)  |  |                                |
| 8a. NAME OF FUNDING/SPONSORING   |       | 8b. OFFICE SYMBOL<br>(If applicable)             | 9. PROCUREMENT INSTRUMENT IDENTIFICATION NUMBER  |  |                                |
| 8c. ADDRESS (City, State, and ZIP Code)  |       |  | 10. SOURCE OF FUNDING NUMBERS  |  |                                |
|  |       |  | PROGRAM<br>ELEMENT NO.   | PROJECT<br>NO.                                     | TASK<br>NO.                    |
|  |       |  | WORK UNIT<br>ACCESSION NO.   |  |                                |
| 11. TITLE (Include Security Classification)<br>Compatibility of Elastomeric Seal Compounds with MIL-H-6083 and MIL-H-46170 Hydraulic Fluids (U)  |       |  |  |  |                                |
| 12. PERSONAL AUTHOR(S)<br>Paul E. Gatza  |       |  |  |  |                                |
| 13a. TYPE OF REPORT<br>Final   |       | 13b. TIME COVERED<br>FROM 12/88 TO 01/90         |  | 14. DATE OF REPORT (Year, Month, Day)<br>June 1990 |                                |
| 15. PAGE COUNT<br>33   |       |  |  |  |                                |
| 16. SUPPLEMENTARY NOTATION   |       |  |  |  |                                |
| 17. COSATI CODES   |       |  | 18. SUBJECT TERMS (Continue on reverse if necessary and identify by block number)                  |  |                                |
| FIELD  | GROUP | SUB-GROUP  | Hydraulic Fluids, Elastomers, Seals, O-rings, Physical Properties,<br>Deterioration (JES) ←        |  |                                |
| 19. ABSTRACT (Continue on reverse if necessary and identify by block number)<br><br>This report compares the relative deteriorative effects of typical suppliers' lots of MIL-H-6083 and MIL-H-46170 hydraulic fluids on off-the-shelf elastomeric seal and O-ring compounds. Comparisons are also made with results obtained using NBR-L, a reference material cited in AMS 3217. |       |  |  |  |                                |
| 20. DISTRIBUTION/AVAILABILITY OF ABSTRACT<br><input checked="" type="checkbox"/> UNCLASSIFIED/UNLIMITED <input type="checkbox"/> SAME AS REPORT <input type="checkbox"/> DTIC USERS  |       |  | 21. ABSTRACT SECURITY CLASSIFICATION<br>Unclassified   |  |                                |
| 22a. NAME OF RESPONSIBLE INDIVIDUAL<br>Paul E. Gatza   |       |  | 22b. TELEPHONE (Include Area Code)<br>703-664-5488   |  | 22c. Office Symbol<br>STRBE-VU |

## PREFACE

This report details investigations conducted and results obtained in efforts to compare the relative deteriorative effects of typical suppliers' lots of MIL-H-6083 and MIL-H-46170 hydraulic fluids on off-the-shelf elastomeric seal compounds obtained from various vendors. Concurrent comparative studies were conducted using NBR-L, a standard reference compound cited in Aerospace Materials Specification (AMS) 3217. Volume change data for each of the fluid/seal compound iterations were supplemented by measurement of ultimate deteriorated physical properties—tensile strength, elongation, modulus, and hardness. Significant observations made and conclusions derived are summarized herein.

Acknowledgement is given to PVT Michael Robinson, who performed the laboratory seal/compound/fluid immersion testing, and to all seal vendors who supplied the compounds used in this work.

# TABLE OF CONTENTS

|                                     | Page |
|-------------------------------------|------|
| SECTION I BACKGROUND.....           | 1    |
| SECTION II INVESTIGATION .....      | 2    |
| Materials Used.....                 | 2    |
| Tests Conducted .....               | 3    |
| Results .....                       | 3    |
| SECTION III DISCUSSION .....        | 4    |
| Performance Factors.....            | 4    |
| Original Physical Properties.....   | 4    |
| Data Translation .....              | 4    |
| Interpretation of Data .....        | 4    |
| Tensile Product.....                | 5    |
| Volume Change .....                 | 5    |
| Mixed Immersions.....               | 6    |
| Graphed Data.....                   | 6    |
| SECTION IV CONCLUSIONS.....         | 8    |
| APPENDIX OF TABLES AND FIGURES..... | A-1  |



|                    |                                     |
|--------------------|-------------------------------------|
| Accession For      |                                     |
| NTIS GRA&I         | <input checked="" type="checkbox"/> |
| DTIC TAB           | <input type="checkbox"/>            |
| Unannounced        | <input type="checkbox"/>            |
| Justification      |                                     |
| By                 |                                     |
| Distribution/      |                                     |
| Availability Codes |                                     |
| Dist               | Avail and/or Special                |
| A-1                |                                     |

## SECTION I. BACKGROUND

The degree of adequacy employed in military specifications for hydraulic fluids when attempting to correlate fluid performance criteria with those of system seals and O-rings has often been questioned. Specifications for seals are quite comprehensive, citing both requirements for original physical characteristics and limitations on the amount of acceptable deterioration after a period of seal/fluid exposure under accelerated conditions. Hydraulic fluid specifications properly reference essential factors such as the chemical nature of constituents, viscosity, and other flow-related parameters. At most, these documents only casually consider the critical elastomeric components of hydraulic systems. This is usually in the form of a limiting value for volume change at a specified temperature, usually 70°C, of a standard reference material such as NBR-L, cited in AMS 3217. Obviously, requirements for fluids and for seals are both dictated by the needs of the particular hydraulic system-configuration, operating temperatures, and pressures encountered. The formulations for the NBR-L and other reference compounds have remained unchanged for several years, while seal suppliers have continually upgraded their product's performance. Thus, it is felt that volume change requirements of the fluid specifications are meaningless. A gap may have been created between the two interdependent and highly-specialized fields of seal and hydraulic fluid formulation.

Voluntary consensus standards organizations in the elastomer, POL, and related fluids areas—such as SAE Committees G-4 and A-6, and ASTM Committees D-11 and D-2—have recently increased their efforts to promote mutual understanding of the complexities of rubber/fluid compatibility. *Ad-hoc* committees comprised of members from both sides have been formed and, when possible, joint sessions of the relevant main committees have been held. Concurrently, fluid compatibility studies, such as detailed herein, have been conducted to ascertain areas of agreement and disagreement relative to fluid and seal specification performance criteria.

## SECTION II. INVESTIGATION

### MATERIALS USED

Examples of typical seal compounds, furnished as ASTM test slabs, were solicited from industry suppliers. A total of 17 materials encompassing nitrile, silicone, and fluorocarbon were received from the following sources:

|                               |                  |
|-------------------------------|------------------|
| <i>CR Industries</i>          | Elgin, IL        |
| <i>Federal Mogul</i>          | Detroit, MI      |
| <i>International Packings</i> | Bristol, NH      |
| <i>John Crane</i>             | Morton Grove, IL |
| <i>Parker Seal</i>            | Lexington, KY    |
| <i>Precision Rubber</i>       | Lebanon, TN      |
| <i>Acushnet</i>               | New Bedford, MA  |
| <i>Greene Tweed</i>           | Kulpsville, PA   |

In addition to the above, two other compounds were included: the NBR-L reference compound previously cited, and a hydrogenated nitrile, which was developed in-house for other applications but known to have good fluid resistance properties.

Alphanumeric codes were assigned to all compounds. Numbers are not sequential because other compounds were solicited for concurrent grease studies. Thus, resultant data can be furnished to vendors without violating their proprietary rights.

The nine hydraulic fluids used in the study were categorized according to two types:

- Four fluids (H-6000, H-6001, H-6002, and H-6004) were furnished in accordance with MIL-H-6083, *Hydraulic Fluid, Petroleum Base, For Preservation and Operation*.
- Five fluids (HF-4, HF-12, HF-15, MF-13, and MF-14) were furnished in accordance with MIL-H-46170, *Hydraulic Fluid, Rust Inhibited, Fire-Resistant, Synthetic Hydrocarbon Base*.

## TESTS CONDUCTED

A modified test procedure, based on ASTM D-471, *Test Method for Rubber Property—Effect of Liquids*, was followed. Specimens were immersed for 14 days at 212F (100°C), after which volume change and retention of original physical properties were determined. Specimens were allowed to cool to room temperature while still immersed, and kept under these conditions until weighing and testing were completed. Each fluid/seal combination was run in triplicate. The same micro dumbbell specimens used to determine volume change were then extended to break on an Instron testing machine to obtain physical property change data.

## RESULTS

Data generated in this study are summarized in Tables 1 through 14 (see Appendix). Tensile and modulus retention percentages in Tables 2 through 10 are based on swollen cross-sectional area, as cited in Federal Test Method Standard (FTMS) 601, *Rubber: Sampling and Testing*, Method 6111, *Tensile Strength and Elongation Immediately After Immersion in Liquids*, rather than computed directly as under ASTM D-471. Modulus retention is based on the 200% determination unless otherwise indicated. If specimen average break was less than 100%, no modulus retention could be determined.

## **SECTION III. DISCUSSION**

### **PERFORMANCE FACTORS**

Acceptance criteria used to analyze the test data evolved were:

- Candidate materials shall retain at least 80% of original tensile strength and elongation;
- Modulus and Shore A hardness changes shall not be excessive (i.e., more than 10 hardness points, or greater than 20% modulus change); and
- Volume change shall be confined to a maximum of 10 to 15% swelling, with any sign of shrinkage signifying immediate rejection.

### **ORIGINAL PHYSICAL PROPERTIES**

Examination of the initial physical properties data of Table 1 indicates that typical seal compounds as supplied by the industry tend to display moderate tensile strength, averaging slightly above 2,000 psi. Elongation was generally low, with some compounds having values well below 200%. Shore hardnesses were in the 65 to 86 points range, while 100% or 200% moduli were indicative of a high state of vulcanization. This correlated well with intended application. Sealing effectiveness is contingent upon retention of integrity while allowing a limited degree of "fluidity" to conform to the configuration of the area to be sealed.

### **DATA TRANSLATION**

The extensive data generated are difficult to analyze and discuss as summarized in Tables 2 through 10. Comparisons of seal material performance either within each fluid type (MIL-H-6083 or MIL-H-46170), or between types, would likewise be difficult. For these reasons, Table 11, a 1-page summarization of all negative effects of the test fluids on measured physical properties, was prepared. Here, the numbers 1 through 8 identify changes deemed excessive and thus detrimental to seal performance, using the limits cited in the previous paragraph. Blocks containing no numbers thus signify full acceptability of the fluid/rubber combination identified therein. Use of this convention obviously excludes any reference to the magnitude of nonconformance.

### **INTERPRETATION OF DATA**

Examination of Table 11 reveals the emergence of certain patterns or trends in seal material performance. Compound 8F-29 evidenced only one failure—excessive tensile loss in fluid H-6002—and thus would head any ranking according to preference. Compounds 8F-1, 8F-4, and

8F-5, which displayed shrinkage or essentially very low swelling, would be disqualified for general use. The latter two compounds however, might be considered marginally acceptable for MIL-H-6083 use only, assuming that instances of modulus increase are not deemed critical factors. Compounds 8F-10, 8F-12, and 8F-31 (the NBR-L reference material) displayed practically identical performance patterns. Poor retention of tensile and elongation correlated with excessive swelling and softening (decrease in hardness). Compound 8F-13 was the only compound found failure-free in the MIL-H-6083 grouping. Three candidates—8F-22, 8F-29 and 8F-32—met all criteria in the MIL-H-46170 fluids. Excessive elongation loss was the most frequently observed deficiency, occurring 81 times, and at least once for all compound iterations except 8F-13, 8F-22, 8F-23, 8F-29, and 8F-32. High tensile strength losses and pronounced increases in modulus were the next most frequently occurring type of failure, but never simultaneously within a specific compound/fluid combination. The lower frequency of occurrence and erratic patterns displayed elsewhere in Table 11 are indicative of subtle differences in formulation within the two types of fluids and perhaps a tendency for suppliers to adhere as closely as possible to performance limitations.

## TENSILE PRODUCT

In order to further analyze both the subtle and apparent differences between fluid types and among candidate compounds, Table 12 was prepared. Here, tensile products [percent tensile strength retained *times* percent elongation retained *divided by* 1,000] are presented for all iterations. Table 12 also includes total row averages, MIL-H-6083 fluid averages, MIL-H-46170 averages, and differences according to fluid type. With the exception of compounds 8F-14 and 8F-16, which had statistically equivalent values for both fluid types, higher tensile products were noted for those materials exposed in MIL-H-46170 fluids. Compounds 8F-19 and 8F-22 showed the greatest amount of improved performance in this regard. The previously noted similar and poor performances of compounds 8F-10, 8F-12, and 8F-31 are again evident, while the highest aggregate tensile products are observed for 8F-22 and 8F-23. Performances of 8F-13, 8F-19, 8F-26, and 8F-29 are also considered good.

## VOLUME CHANGE

A similar comparison but based on volume change data is presented in Table 13. A greater amount of swelling in the MIL-H-6083 fluids was noted in all cases except, of course, when shrinkage occurred in either or both types of fluid. Swelling correlated inversely with performance as indicated by tensile product; i.e., low for highly-rated 8F-22 and 8F-23, and extremely high for the worst compounds, such as 8F-10 and 8F-12. The presence of many intermediately grouped differences reflects the inadequacy of basing performance solely on volume change information. Conversely, referring back to Table 12, tensile product data is not always infallible. Relatively good tensile product values for 8F-1, 8F-4, and 8F-5, mask the aforementioned shrinkage. Table 13 also contains a comparison of NBR-L swell data, extracted from fluid suppliers' conformance testing reports, with values obtained in this work. As noted, tests were conducted at 100°C and 70°C,



respectively. The lower exposure temperature used by the suppliers consistently resulted in higher swell values, a sign that choice of test conditions is critical. Additionally, it is known that testing at 100°C may, in some cases, not duplicate certain in-service conditions which may be as much as 20 or 30°C higher, or even lower than the currently referenced 70°C. Insufficient data was generated here to conclusively establish any trends.

## MIXED IMMERSIONS

Table 14 contains the results of a very limited attempt to access the effects of mixed immersion of two compounds, using one MIL-H-6083 and one MIL-H-46170 fluid—H-6002 and HF-15, respectively. Compounds 8F-5 and 8F-12 were immersed in each fluid for 1 week at 100°C and then tested. Ultimate volume changes for both were intermediate, but biased toward the MIL-H-6083 fluid. Hardness change for the 8F-5 was also intermediate but biased toward the MIL-H-46170 fluid, while the loss for 8F-12 after mixed immersion was less than found for either individual exposure. The final tensile product of 8F-12 was only slightly less and the corresponding value for 8F-5 deemed essentially equivalent to that observed when singly immersed for 2 weeks in the MIL-H-46170 fluid (HF-15). Changes in modulus retention paralleled those for hardness—intermediate for 8F-5, but outside of the range found for 8F-12. It is apparent that one cannot assume mixed immersions will always effect an across-the-board intermediate change in all physical properties. Therefore, indiscriminate use or improper citing of correct hydraulic fluids entails a certain amount of risk relative to the adequacy of seal performance.

## GRAPHED DATA

To further emphasize performance differences between MIL-H-6083 and MIL-H-46170 hydraulic fluids and illustrate the shortcomings of NBR-L as a reference elastomer compound in fuel and fluid qualification work, Figures 1 and 2 were prepared (see Appendix pages A-16 and A-17). As indicated in Figure 1, higher tensile product averages for seal compounds exposed to MIL-H-46170 fluids generally correlated with lower volume changes. No compound immersed in MIL-H-6083 fluid evidenced a tensile product greater than 10. This plateau was reached by five materials when exposed to the MIL-H-46170 fluids. An intermediate group of compounds is readily discernable. These, such as 8F-2, 8F-3, 8F-14, and 8F-16, showed low volume changes, but tensile products were only fair. The tendency for compounds displaying shrinkage or very low swelling to generate reasonably good tensile product values (8F-1, 8F-4, and 8F-5) is also evident. Figure 2 compares performance of reference compound NBR-L (8F-31) against all other candidates in each fluid. The magnitude of difference (relatively inferior showing) of the NBR-L is quite apparent, indicating that the compound is not representative of the average quality of off-the-shelf seals. Currently, NBR-L is used to qualify fluids, but solely based on satisfying a stipulated volume change level. Volume change averages for all compounds in each of the fluid type groups were derived from Table 13 and compared with that for NBR-L in the following table:

**Table of Volume Change Averages**

|               | <b>MIL-H-6083</b> | <b>MIL-H-46170</b> |
|---------------|-------------------|--------------------|
| All compounds | 12.06             | 5.22               |
| NBR-L         | 23.90             | 17.15              |
| Difference    | 11.84             | 11.93              |

The above figures include all outliers; i.e., compounds displaying shrinkage or very high swelling (8F-1, 8F-4, 8F-5, 8F-10, and 8F-12). If these were excluded from consideration, compound averages would be lower and the gap even greater. Thus, one would surmise that the state-of-the-art relative to selection of reference compounds is not consistent with the quality of off-the-shelf seal materials. Here, only two classes of hydraulic fluid have been screened. Whether this tendency persists throughout the range of other hydraulic fluid compliance standards is unknown. It is known that AMS 3217, the document citing NBR-L and other standard elastomer compounds, is considered outdated and, as demonstrated in this study, revision is needed.

## SECTION IV. CONCLUSIONS

- Performance of typical suppliers' off-the-shelf seal compounds, in terms of volume change and retention of physical properties, is better in MIL-H-46170 hydraulic fluids than in fluids conforming to MIL-H-6083.
- Reliance on volume change as the sole criterion for seal/fluid compatibility is risky. Extent of swelling or shrinkage does not always correlate with exposure-inflicted deterioration in tensile strength and elongation, changes in modulus, and hardening or softening.
- The performance of standard reference compound NBR-L, cited in AMS 3217, in both types of hydraulic fluid used in this study was generally inferior to that observed for the representative suppliers' compounds.
- Fluid qualification, based on volume change data from NBR-L immersions, does not sufficiently focus on the actual in-service exposure conditions typically encountered.
- Use of one reference test temperature (70° or 100°C) may be inadequate to accurately assess potential in-service performance. Limited comparisons derived from this work indicate that volume changes at elevated temperatures are lower than at the cited levels.
- Likewise, use of one volume swell limit (such as 15% minimum swell) for differing classes or types of hydraulic fluid may, in some instances, be unrealistic.
- Alternating exposure of elastomeric seals to hydraulic fluids satisfying dissimilar qualification standards may effect synergistic changes in physical properties, rather than the assumed intermediate changes.

## APPENDIX OF TABLES AND FIGURES

| Table             | Caption   | Page |
|-------------------|---|------|
| 1                 | Original Physical Properties—Fluid-Resistant Compounds.....                     | A-2  |
| 2                 | Retention of Properties—Fluid H-6000.....                                       | A-3  |
| 3                 | Retention of Properties—Fluid H-6001.....                                       | A-4  |
| 4                 | Retention of Properties—Fluid H-6002.....                                       | A-5  |
| 5                 | Retention of Properties—Fluid H-6004.....                                       | A-6  |
| 6                 | Retention of Properties—Fluid HF-4.....   | A-7  |
| 7                 | Retention of Properties—Fluid HF-12.....  | A-8  |
| 8                 | Retention of Properties—Fluid HF-15.....  | A-9  |
| 9                 | Retention of Properties—Fluid MF-13.....  | A-10 |
| 10                | Retention of Properties—Fluid MF-14.....  | A-11 |
| 11                | Effect of Fluids on Physical Properties.....                                    | A-12 |
| 12                | Seal/Fluid Compatibility—Tensile Product.....                                   | A-13 |
| 13                | Seal/Fluid Compatibility—Volume Change .....                                    | A-14 |
| 14                | Retention of Properties—Mixed Fluid Immersion .....                             | A-15 |
| <br><b>Figure</b> |   |      |
| 1                 | Tensile Product and Volume Change Averages,<br>MIL-H-6083 vs. MIL-H-46170 ..... | A-16 |
| 2                 | Tensile Product and Volume Change, NBR-L vs. Group Average .....                | A-17 |

**Table 1. Original Physical Properties—Fluid-Resistant Compounds**

| Compound | Tensile Str.<br>psi | Elong.<br>% | 100% Mod.<br>psi | 200% Mod.<br>psi | Hardness<br>Shore A |
|----------|---------------------|-------------|------------------|------------------|---------------------|
| 8F-1     | 2500.00             | 211.00      | 1390.00          | 2425.00          | 77.00               |
| 8F-2     | 2603.00             | 389.00      | 587.00           | 1525.00          | 69.00               |
| 8F-3     | 2487.00             | 140.00      | 1812.00          | —                | 80.00               |
| 8F-4     | 2230.00             | 178.00      | 1260.00          | —                | 67.00               |
| 8F-5     | 1990.00             | 178.00      | 1137.00          | —                | 68.00               |
| 8F-9     | 2705.00             | 531.00      | 612.00           | 797.00           | 69.00               |
| 8F-10    | 1211.00             | 149.00      | 991.00           | —                | 79.00               |
| 8F-12    | 2160.00             | 272.00      | 810.00           | 1713.00          | 66.00               |
| 8F-13    | 1916.00             | 170.00      | 1170.00          | —                | 75.00               |
| 8F-14    | 1802.00             | 142.00      | 1290.00          | —                | 74.00               |
| 8F-16    | 1981.00             | 73.00       | —                | —                | 86.00               |
| 8F-19    | 1983.00             | 204.00      | 970.00           | 1985.00          | 69.00               |
| 8F-22    | 1934.00             | 281.00      | 806.00           | 1413.00          | 70.00               |
| 8F-23    | 1761.00             | 166.00      | 1260.00          | —                | 74.00               |
| 8F-26    | 2054.00             | 250.00      | 824.00           | 1823.00          | 65.00               |
| 8F-27    | 1930.00             | 120.00      | 1540.00          | —                | 84.00               |
| 8F-29    | 1995.00             | 86.00       | 1302.00          | —                | 79.00               |
| 8F-31    | 2896.00             | 242.00      | 1033.00          | 2428.00          | 71.00               |
| 8F-32    | 4967.00             | 484.00      | 588.00           | 1095.00          | 80.00               |

**Table 2. Retention of Properties—Fluid H-6000**

| Compound | Tensile Ret.<br>% | Elong. Ret.<br>% | 200% Mod.<br>Ret. - % | Hard. Chge.<br>pts. | Vol. Chge.<br>% |
|----------|-------------------|------------------|-----------------------|---------------------|-----------------|
| 8F-1     | 111.47            | 65.88            | *167.86               | 11.00               | -9.56           |
| 8F-2     | 97.10             | 75.32            | 124.94                | -1.00               | 7.78            |
| 8F-3     | 89.42             | 50.71            | —                     | -6.00               | 8.14            |
| 8F-4     | 105.10            | 85.96            | *131.03               | -2.00               | 5.31            |
| 8F-5     | 105.47            | 80.34            | *133.46               | .00                 | 3.03            |
| 8F-9     | 83.06             | 72.50            | 115.01                | -4.00               | 9.02            |
| 8F-10    | 48.21             | 67.11            | *58.92                | -20.00              | 63.06           |
| 8F-12    | 66.19             | 63.97            | *133.46               | -15.00              | 24.77           |
| 8F-13    | 105.82            | 91.18            | *116.67               | -5.00               | 7.67            |
| 8F-14    | 94.16             | 70.42            | *129.84               | -5.00               | 8.63            |
| 8F-16    | 96.67             | 82.19            | —                     | -5.00               | 9.46            |
| 8F-19    | 65.03             | 78.92            | *84.01                | -5.00               | 9.73            |
| 8F-22    | 72.51             | 100.36           | 65.20                 | -5.00               | 7.21            |
| 8F-23    | 68.79             | 122.89           | *69.54                | -4.00               | 4.44            |
| 8F-26    | 80.33             | 50.00            | *144.70               | -6.00               | 14.50           |
| 8F-27    | 77.13             | 64.17            | —                     | -4.00               | 6.45            |
| 8F-29    | 89.40             | 98.84            | —                     | -7.00               | 10.82           |
| 8F-31    | 56.90             | 63.64            | *98.19                | -15.00              | 20.87           |
| 8F-32    | 76.87             | 92.15            | 94.63                 | -8.00               | 14.63           |

\* = 100% Mod.

**Table 3. Retention of Properties—Fluid H-6001**

| <b>Compound</b> | <b>Tensile Ret.<br/>%</b> | <b>Elong. Ret.<br/>%</b> | <b>200% Mod.<br/>Ret. - %</b> | <b>Hard. Chge.<br/>pts.</b> | <b>Vol. Chge.<br/>%</b> |
|-----------------|---------------------------|--------------------------|-------------------------------|-----------------------------|-------------------------|
| 8F-1            | 107.12                    | 70.62                    | *148.78                       | 11.00                       | -8.72                   |
| 8F-2            | 95.59                     | 81.23                    | 108.85                        | -1.00                       | 8.42                    |
| 8F-3            | 74.80                     | 70.71                    | —                             | -4.00                       | 7.90                    |
| 8F-4            | 103.33                    | 87.64                    | *116.07                       | -1.00                       | 6.69                    |
| 8F-5            | 103.15                    | 85.39                    | *117.76                       | 1.00                        | 4.06                    |
| 8F-9            | 78.37                     | 82.49                    | 101.02                        | -2.00                       | 9.04                    |
| 8F-10           | 48.91                     | 46.31                    | —                             | -18.00                      | 65.25                   |
| 8F-12           | 72.44                     | 77.21                    | 88.46                         | -12.00                      | 27.08                   |
| 8F-13           | 106.68                    | 91.76                    | *106.24                       | -6.00                       | 8.93                    |
| 8F-14           | 99.22                     | 85.21                    | *112.28                       | -5.00                       | 10.06                   |
| 8F-16           | 101.02                    | 90.41                    | —                             | -6.00                       | 9.26                    |
| 8F-19           | 78.88                     | 92.16                    | *85.36                        | -4.00                       | 3.46                    |
| 8F-22           | 86.81                     | 110.32                   | 76.58                         | -7.00                       | 4.87                    |
| 8F-23           | 75.96                     | 138.55                   | *67.35                        | -6.00                       | 3.99                    |
| 8F-26           | 77.33                     | 150.00                   | 57.40                         | -11.00                      | 15.64                   |
| 8F-27           | 87.40                     | 66.67                    | —                             | -5.00                       | 8.67                    |
| 8F-29           | 88.72                     | 105.81                   | —                             | -7.00                       | 12.35                   |
| 8F-31           | 60.77                     | 70.25                    | *84.31                        | -16.00                      | 25.42                   |
| 8F-32           | 71.64                     | 95.45                    | 84.57                         | -8.00                       | 16.11                   |

\* = 100% Mod.

**Table 4. Retention of Properties—Fluid H-6002**

| Compound | Tensile Ret.<br>% | Elong. Ret.<br>% | 200% Mod.<br>Ret. - % | Hard. Chge.<br>pts. | Vol. Chge.<br>% |
|----------|-------------------|------------------|-----------------------|---------------------|-----------------|
| 8F-1     | 120.10            | 87.20            | *150.95               | 7.00                | -12.39          |
| 8F-2     | 94.17             | 71.98            | 123.28                | -3.00               | 7.92            |
| 8F-3     | 79.67             | 70.00            | —                     | -7.00               | 10.36           |
| 8F-4     | 101.34            | 85.96            | *120.88               | -3.00               | 7.26            |
| 8F-5     | 102.98            | 80.34            | *126.79               | -1.00               | 4.33            |
| 8F-9     | 76.24             | 79.47            | 97.55                 | -6.00               | 8.90            |
| 8F-10    | 47.39             | 36.91            | —                     | -21.00              | 65.45           |
| 8F-12    | 69.85             | 66.18            | *113.56               | -14.00              | 27.91           |
| 8F-13    | 106.82            | 90.59            | *115.03               | -6.00               | 8.94            |
| 8F-14    | 85.45             | 64.08            | —                     | -4.00               | 10.51           |
| 8F-16    | 94.48             | 79.45            | —                     | 1.00                | 9.62            |
| 8F-19    | 89.80             | 114.22           | 85.63                 | -1.00               | 1.79            |
| 8F-22    | 95.10             | 106.05           | 86.82                 | -4.00               | 2.36            |
| 8F-23    | 83.61             | 114.46           | *83.07                | -2.00               | 1.49            |
| 8F-26    | 78.45             | 138.40           | 60.74                 | -10.00              | 15.21           |
| 8F-27    | 88.81             | 78.33            | —                     | -5.00               | 7.71            |
| 8F-29    | 68.63             | 80.23            | —                     | -7.00               | 12.61           |
| 8F-31    | 53.59             | 58.68            | *99.13                | -18.00              | 25.74           |
| 8F-32    | 74.88             | 90.08            | 90.07                 | -9.00               | 16.50           |

\* = 100% Mod.



**Table 5. Retention of Properties—Fluid H-6004**

| Compound | Tensile Ret.<br>% | Elong. Ret.<br>% | 200% Mod.<br>Ret. - % | Hard. Chge.<br>pts. | Vol. Chge.<br>% |
|----------|-------------------|------------------|-----------------------|---------------------|-----------------|
| 8F-1     | 111.41            | 78.67            | *147.98               | 12.00               | -8.97           |
| 8F-2     | 100.01            | 82.26            | 121.38                | -2.00               | 7.62            |
| 8F-3     | 89.86             | 77.14            | *109.91               | -5.00               | 8.73            |
| 8F-4     | 99.65             | 88.76            | *116.66               | -1.00               | 5.36            |
| 8F-5     | 101.27            | 87.64            | *118.08               | 1.00                | 2.97            |
| 8F-9     | 76.80             | 80.79            | 94.34                 | -3.00               | 9.34            |
| 8F-10    | 44.26             | 52.35            | —                     | -18.00              | 65.17           |
| 8F-12    | 67.56             | 76.84            | 82.87                 | -5.00               | 23.94           |
| 8F-13    | 100.59            | 97.06            | *100.55               | -4.00               | 7.29            |
| 8F-14    | 98.11             | 88.73            | *109.90               | -4.00               | 8.17            |
| 8F-16    | 85.22             | 80.82            | —                     | -3.00               | 8.26            |
| 8F-19    | 57.14             | 87.25            | *69.79                | -2.00               | 4.24            |
| 8F-22    | 78.28             | 103.20           | 73.18                 | -6.00               | 5.40            |
| 8F-23    | 64.61             | 138.55           | *61.56                | -6.00               | 4.55            |
| 8F-26    | 75.15             | 142.00           | 56.33                 | -7.00               | 13.44           |
| 8F-27    | 76.55             | 80.00            | —                     | .00                 | 5.48            |
| 8F-29    | 86.78             | 108.14           | —                     | -4.00               | 10.10           |
| 8F-31    | 49.42             | 63.64            | *80.20                | -14.00              | 23.55           |
| 8F-32    | 74.39             | 93.18            | 88.17                 | -11.00              | 14.87           |

\* = 100% Mod.

**Table 6. Retention of Properties—Fluid HF-4**

| Compound | Tensile Ret.<br>% | Elong. Ret.<br>% | 200% Mod.<br>Ret. - % | Hard. Chge.<br>pts. | Vol. Chge.<br>% |
|----------|-------------------|------------------|-----------------------|---------------------|-----------------|
| 8F-1     | 116.58            | 74.41            | *78.18                | 11.00               | -10.93          |
| 8F-2     | 103.64            | 70.95            | 142.53                | 2.00                | 3.71            |
| 8F-3     | 89.68             | 72.86            | *119.39               | 4.00                | 4.52            |
| 8F-4     | 106.31            | 75.84            | *144.09               | 3.00                | .78             |
| 8F-5     | 119.75            | 79.78            | *153.33               | 5.00                | -2.26           |
| 8F-9     | 87.99             | 78.91            | 114.70                | .00                 | 5.27            |
| 8F-10    | 76.04             | 65.77            | —                     | -14.00              | 20.71           |
| 8F-12    | 83.64             | 69.49            | *124.41               | -12.00              | 17.00           |
| 8F-13    | 111.70            | 82.94            | *133.78               | -3.00               | 3.16            |
| 8F-14    | 100.99            | 71.83            | *138.27               | 1.00                | 3.66            |
| 8F-16    | 101.54            | 72.60            | —                     | -4.00               | 3.94            |
| 8F-19    | 83.43             | 106.86           | 77.02                 | -8.00               | 2.97            |
| 8F-22    | 112.13            | 109.96           | 95.54                 | -5.00               | 3.01            |
| 8F-23    | 83.47             | 138.55           | *75.78                | -7.00               | 2.87            |
| 8F-26    | 83.83             | 123.60           | 70.28                 | -11.00              | 11.90           |
| 8F-27    | 85.02             | 67.50            | —                     | .00                 | 2.48            |
| 8F-29    | 95.40             | 97.67            | —                     | -5.00               | 6.03            |
| 8F-31    | 76.14             | 72.73            | *105.95               | -14.00              | 17.97           |
| 8F-32    | 85.18             | 81.61            | 119.64                | -6.00               | 11.30           |

\* = 100% Mod.

**Table 7. Retention of Properties—Fluid HF-12**

| Compound | Tensile Ret.<br>% | Elong. Ret.<br>% | 200% Mod.<br>Ret. - % | Hard. Chge.<br>pts. | Vol. Chge.<br>% |
|----------|-------------------|------------------|-----------------------|---------------------|-----------------|
| 8F-1     | 116.58            | 74.41            | *78.18                | 11.00               | -10.93          |
| 8F-2     | 103.64            | 70.95            | 142.53                | 2.00                | 3.71            |
| 8F-3     | 89.68             | 72.86            | *119.30               | 4.00                | 4.52            |
| 8F-4     | 106.31            | 75.84            | *144.00               | 3.00                | .78             |
| 8F-5     | 119.75            | 79.78            | *153.30               | 5.00                | -2.26           |
| 8F-9     | 87.99             | 78.91            | 114.70                | .00                 | 5.27            |
| 8F-10    | 76.04             | 65.77            | —                     | -14.00              | 20.71           |
| 8F-12    | 83.64             | 69.49            | 124.41                | -12.00              | 17.00           |
| 8F-13    | 111.70            | 82.94            | *133.78               | -3.00               | 3.16            |
| 8F-14    | 100.99            | *71.83           | 138.27                | 1.00                | 3.66            |
| 8F-16    | 101.54            | 72.60            | —                     | -4.00               | 3.94            |
| 8F-19    | 83.43             | 106.86           | 77.02                 | -8.00               | 2.97            |
| 8F-22    | 112.13            | 109.96           | 95.54                 | -5.00               | 3.01            |
| 8F-23    | 83.47             | 138.55           | *75.78                | -7.00               | 2.87            |
| 8F-26    | 83.83             | 123.60           | *70.28                | -11.00              | 11.90           |
| 8F-27    | 85.02             | 67.50            | —                     | .00                 | 2.48            |
| 8F-29    | 95.40             | 97.67            | —                     | -5.00               | 6.03            |
| 8F-31    | 76.14             | 72.73            | *105.95               | -14.00              | 17.97           |
| 8F-32    | 85.18             | 81.61            | 119.64                | -6.00               | 11.30           |

\* = 100% Mod.

**Table 8. Retention of Properties—Fluid HF-15**

| Compound | Tensile Ret.<br>% | Elong. Ret.<br>% | 200% Mod.<br>Ret. - % | Hard. Chge.<br>pts. | Vol. Chge.<br>% |
|----------|-------------------|------------------|-----------------------|---------------------|-----------------|
| 8F-1     | 121.41            | 67.30            | *184.26               | 6.00                | -11.15          |
| 8F-2     | 105.29            | 81.23            | 128.82                | -2.00               | 3.49            |
| 8F-3     | 91.09             | 69.29            | —                     | -1.00               | 3.50            |
| 8F-4     | 114.73            | 87.64            | *136.51               | 3.00                | - .61           |
| 8F-5     | 114.92            | 76.97            | *152.23               | 6.00                | -3.00           |
| 8F-9     | 76.74             | 80.98            | 100.26                | -1.00               | 5.48            |
| 8F-10    | 77.39             | 73.15            | *91.98                | -14.00              | 20.11           |
| 8F-12    | 89.85             | 80.15            | 105.22                | -10.00              | 15.22           |
| 8F-13    | 117.22            | 90.00            | *127.23               | -4.00               | 1.77            |
| 8F-14    | 103.26            | 73.24            | *132.59               | 1.00                | 1.63            |
| 8F-16    | 105.09            | 82.19            | —                     | -2.00               | 3.49            |
| 8F-19    | 91.86             | 114.22           | 83.35                 | -4.00               | 2.59            |
| 8F-22    | 103.41            | 114.59           | 86.98                 | -5.00               | 1.96            |
| 8F-23    | 84.94             | 138.55           | *77.35                | 4.00                | 2.23            |
| 8F-26    | 105.00            | 58.40            | *171.96               | -4.00               | 8.70            |
| 8F-27    | 89.73             | 77.50            | —                     | 3.00                | .71             |
| 8F-29    | 102.14            | 115.12           | —                     | .00                 | 2.91            |
| 8F-31    | 76.38             | 74.38            | *101.13               | -7.00               | 16.55           |
| 8F-32    | 84.29             | 90.50            | 108.06                | -3.00               | 10.80           |

\* = 100% Mod.

**Table 9. Retention of Properties—Fluid MF-13**

| <b>Compound</b> | <b>Tensile Ret.<br/>%</b> | <b>Elong. Ret.<br/>%</b> | <b>200% Mod.<br/>Ret. - %</b> | <b>Hard. Chge.<br/>pts.</b> | <b>Vol. Chge.<br/>%</b> |
|-----------------|---------------------------|--------------------------|-------------------------------|-----------------------------|-------------------------|
| 8F-1            | 123.60                    | 79.15                    | *171.38                       | 13.00                       | -11.00                  |
| 8F-2            | 103.95                    | 76.35                    | 133.18                        | .00                         | 3.64                    |
| 8F-3            | 92.24                     | 75.00                    | *121.07                       | -2.00                       | 4.08                    |
| 8F-4            | 111.05                    | 76.97                    | *148.51                       | 4.00                        | .22                     |
| 8F-5            | 120.99                    | 78.65                    | *158.80                       | 6.00                        | -2.28                   |
| 8F-9            | 85.53                     | 80.60                    | 115.06                        | -3.00                       | 6.44                    |
| 8F-10           | 78.09                     | 64.43                    | —                             | -12.00                      | 20.52                   |
| 8F-12           | 85.85                     | 71.32                    | *119.46                       | -9.00                       | 15.30                   |
| 8F-13           | 118.31                    | 88.24                    | *131.63                       | -1.00                       | 2.14                    |
| 8F-14           | 105.74                    | 70.42                    | *142.60                       | 3.00                        | 2.65                    |
| 8F-16           | 108.97                    | 76.71                    | —                             | -1.00                       | 3.52                    |
| 8F-19           | 94.94                     | 117.16                   | 86.03                         | -3.00                       | 2.67                    |
| 8F-22           | 98.07                     | 104.98                   | 92.93                         | -3.00                       | 2.17                    |
| 8F-23           | 84.94                     | 141.57                   | *76.13                        | -2.00                       | 2.64                    |
| 8F-26           | 92.28                     | 140.00                   | 69.02                         | -7.00                       | 10.02                   |
| 8F-27           | 100.00                    | 67.50                    | —                             | 4.00                        | 1.32                    |
| 8F-29           | 95.77                     | 97.67                    | —                             | .00                         | 3.50                    |
| 8F-31           | 72.91                     | 64.05                    | *117.55                       | -10.00                      | 16.95                   |
| 8F-32           | 78.65                     | 84.50                    | 113.54                        | -4.00                       | 15.04                   |

\* = 100% Mod.

**Table 10. Retention of Properties—Fluid MF-14**

| Compound | Tensile Ret.<br>% | Elong. Ret.<br>% | 200% Mod.<br>Ret. - % | Hard. Chge.<br>pts. | Vol. Chge.<br>% |
|----------|-------------------|------------------|-----------------------|---------------------|-----------------|
| 8F-1     | 123.05            | 85.31            | *161.31               | 13.00               | -11.10          |
| 8F-2     | 105.33            | 79.18            | 129.87                | 2.00                | 3.92            |
| 8F-3     | 93.60             | 77.86            | *121.73               | 2.00                | 4.68            |
| 8F-4     | 111.09            | 84.27            | *134.78               | 3.00                | 1.13            |
| 8F-5     | 111.51            | 80.34            | *137.66               | 3.00                | -1.55           |
| 8F-9     | 88.28             | 84.75            | 107.53                | -4.00               | 5.83            |
| 8F-10    | 79.34             | 79.87            | *89.65                | -11.00              | 22.65           |
| 8F-12    | 87.71             | 79.78            | 102.97                | -9.00               | 16.86           |
| 8F-13    | 124.07            | 99.41            | *124.76               | -7.00               | 3.86            |
| 8F-14    | 95.60             | 71.13            | *132.03               | 3.00                | 3.26            |
| 8F-16    | 83.42             | 68.49            | —                     | -2.00               | 4.52            |
| 8F-19    | 67.94             | 114.71           | 66.24                 | -4.00               | 3.10            |
| 8F-22    | 116.21            | 120.28           | 87.78                 | 3.00                | 2.38            |
| 8F-23    | 83.03             | 148.80           | *76.17                | -4.00               | 2.56            |
| 8F-26    | 81.66             | 201.60           | 91.70                 | -8.00               | 11.36           |
| 8F-27    | 82.53             | 59.17            | —                     | -10.00              | 2.47            |
| 8F-29    | 94.39             | 104.65           | —                     | -2.00               | 4.64            |
| 8F-31    | 72.34             | 73.97            | *95.69                | -12.00              | 18.35           |
| 8F-32    | 88.01             | 93.80            | 102.52                | -4.00               | 11.76           |

\* = 100% Mod.

**Table 11. Effect of Fluids on Physical Properties**

| ID    | MIL-H-6083 Fluids |            |            |            | MIL-H-46170 Fluids |            |            |            |            |
|-------|-------------------|------------|------------|------------|--------------------|------------|------------|------------|------------|
|       | H-6000            | H-6001     | H-6002     | H-6004     | HF-4               | HF-12      | HF-15      | MF-13      | MF-14      |
| 8F-1  | 2, 3, 5, 7        | 2, 3, 5, 7 | 3, 5       | 3, 5       | 2, 3, 5, 7         | 2, 3, 5, 7 | 2, 3, 5    | 2, 3, 5, 7 | 3, 5, 7    |
| 8F-2  | 2, 3              | 1, 2       | 3          | 3          | 2, 3               | 2, 3       | 3          | 2, 3       | 2, 3       |
| 8F-3  | 2                 | 1, 2       | 1, 2       | 2          | 2                  | 2          | 2          | 2, 3       | 2, 3       |
| 8F-4  | 3                 |            |            |            | 2, 3               | 2, 3       | 3, 5       | 2, 3       | 3          |
| 8F-5  | 3                 |            | 3          |            | 2, 3, 5            | 2, 3, 5    | 2, 3, 5    | 2, 3, 5    | 3, 5       |
| 8F-9  | 2                 | 1          | 1, 2       | 1          | 2                  | 2          | 1          |            |            |
| 8F-10 | 1, 2, 4, 6, 8     | 1, 2, 6, 8 | 1, 2, 6, 8 | 1, 2, 6, 8 | 1, 2, 6, 8         | 1, 2, 6, 8 | 1, 2, 6, 8 | 1, 2, 6, 8 | 1, 2, 6, 8 |
| 8F-12 | 1, 2, 6, 8        | 1, 2, 6, 8 | 1, 2, 6, 8 | 1, 2, 6    | 2, 3, 6, 8         | 2, 3, 6, 8 | 8          | 2          | 2, 6       |
| 8F-13 |                   |            |            |            | 3                  | 3          | 3          | 3          | 3          |
| 8F-14 | 2, 3              |            | 2          |            | 2, 3               | 2, 3       | 2, 3       | 2, 3       | 2, 3       |
| 8F-16 |                   |            | 2          |            | 2                  | 2          |            | 2          | 2          |
| 8F-19 | 1, 2              | 1          |            | 1, 4       | 4                  | 4          |            |            | 4          |
| 8F-22 | 1, 4              | 4          |            | 1, 4       |                    |            |            |            |            |
| 8F-23 | 1, 4              | 1, 4       |            | 1, 4       | 4                  | 4          | 4          | 4          | 4          |
| 8F-26 | 2, 3              | 1, 4, 8    | 1, 4, 8    | 1, 4       | 4, 8               | 4, 8       | 2, 3       | 4          |            |
| 8F-27 | 1, 2              | 2          | 2          | 1          | 2                  | 2          | 2          | 2          | 2          |
| 8F-29 |                   |            | 1          |            |                    |            |            |            |            |
| 8F-31 | 1, 2, 6, 8        | 1, 2, 6, 8 | 1, 2, 6, 8 | 1, 2, 6, 8 | 1, 2, 6, 8         | 1, 2, 6, 8 | 1, 2, 6    | 1, 2, 6    | 1, 2, 6, 8 |
| 8F-32 | 1                 | 1          | 1, 6       | 1, 8       |                    |            |            |            |            |

- 1 = excessive tensile loss
- 2 = excessive elongation loss
- 3 = excessive modulus increase
- 4 = excessive modulus decrease
- 5 = shrinkage
- 6 = excessive swelling
- 7 = excessive hardness increase
- 8 = excessive hardness decrease

**Table 12. Seal/Fluid Compatibility—Tensile Product**

| Comp. | MIL-H-6083 Fluids |                 |               |        | MIL-H-46170 Fluids |       |       |       |       |
|-------|-------------------|-----------------|---------------|--------|--------------------|-------|-------|-------|-------|
|       | H-6000            | H-6001          | H-6002        | H-6004 | HF-4               | HF-12 | HF-15 | MF-13 | MF-14 |
| 8F-1  | 7.34              | 7.56            | 10.47         | 8.76   | 8.67               | 9.33  | 8.17  | 9.78  | 10.50 |
| 8F-2  | 7.31              | 7.76            | 6.78          | 8.23   | 7.35               | 8.23  | 8.55  | 7.94  | 8.34  |
| 8F-3  | 4.53              | 5.29            | 5.58          | 6.93   | 6.53               | 6.48  | 6.31  | 6.92  | 7.29  |
| 8F-4  | 9.03              | 9.06            | 8.71          | 8.85   | 8.06               | 10.21 | 10.05 | 8.55  | 9.36  |
| 8F-5  | 8.47              | 8.81            | 8.27          | 8.88   | 9.55               | 9.64  | 8.85  | 9.52  | 8.96  |
| 8F-9  | 6.02              | 6.46            | 6.06          | 6.20   | 6.94               | 7.84  | 6.21  | 6.89  | 7.48  |
| 8F-10 | 3.24              | 2.26            | 1.75          | 2.32   | 5.00               | 4.87  | 5.66  | 5.03  | 6.34  |
| 8F-12 | 4.23              | 5.59            | 4.62          | 5.19   | 5.81               | 7.16  | 7.20  | 6.12  | 7.00  |
| 8F-13 | 9.65              | 9.79            | 9.68          | 9.76   | 9.26               | 10.32 | 10.55 | 10.44 | 12.33 |
| 8F-14 | 6.63              | 8.45            | 5.48          | 8.71   | 7.25               | 7.49  | 7.56  | 7.45  | 6.80  |
| 8F-16 | 7.95              | 9.13            | 7.51          | 6.89   | 7.37               | 9.23  | 8.64  | 8.36  | 5.71  |
| 8F-19 | 5.13              | 7.27            | 10.26         | 4.99   | 8.92               | 12.25 | 10.49 | 11.12 | 7.79  |
| 8F-22 | 7.28              | 9.58            | 10.08         | 8.08   | 12.33              | 13.20 | 11.85 | 10.30 | 13.98 |
| 8F-23 | 8.45              | 10.52           | 9.57          | 8.95   | 11.57              | 12.68 | 11.77 | 12.02 | 12.35 |
| 8F-26 | 4.02              | 11.60           | 10.86         | 10.67  | 10.36              | 7.45  | 6.13  | 12.92 | 16.46 |
| 8F-27 | 4.95              | 5.83            | 6.96          | 6.12   | 5.74               | 6.92  | 6.95  | 6.75  | 4.88  |
| 8F-29 | 8.84              | 9.39            | 5.51          | 9.38   | 9.32               | 10.92 | 11.76 | 9.35  | 9.88  |
| 8F-31 | 3.62              | 4.27            | 3.14          | 3.14   | 5.54               | 5.58  | 5.68  | 4.67  | 5.35  |
| 8F-32 | 7.08              | 6.84            | 6.75          | 6.93   | 6.95               | 7.66  | 7.63  | 6.65  | 8.26  |
| Avg.  | 6.51              | 7.66            | 7.26          | 7.32   | 8.03               | 8.81  | 8.42  | 8.46  | 8.90  |
|       | Row<br>Avg.       | H Fluid<br>Avg. | HF/MF<br>Avg. | Diff.  |                    |       |       |       |       |
| 8F-1  | 8.96              | 8.54            | 9.29          | .76    |                    |       |       |       |       |
| 8F-2  | 7.83              | 7.52            | 8.08          | .56    |                    |       |       |       |       |
| 8F-3  | 6.21              | 5.58            | 6.71          | 1.13   |                    |       |       |       |       |
| 8F-4  | 9.10              | 8.91            | 9.25          | .34    |                    |       |       |       |       |
| 8F-5  | 8.99              | 8.61            | 9.30          | .70    |                    |       |       |       |       |
| 8F-9  | 6.68              | 6.19            | 7.07          | .89    |                    |       |       |       |       |
| 8F-10 | 4.05              | 2.39            | 5.38          | 2.99   |                    |       |       |       |       |
| 8F-12 | 5.88              | 4.91            | 6.66          | 1.75   |                    |       |       |       |       |
| 8F-13 | 10.20             | 9.72            | 10.58         | .86    |                    |       |       |       |       |
| 8F-14 | 7.31              | 7.32            | 7.31          | -.01   |                    |       |       |       |       |
| 8F-16 | 7.87              | 7.87            | 7.86          | -.01   |                    |       |       |       |       |
| 8F-19 | 8.69              | 6.91            | 10.11         | 3.20   |                    |       |       |       |       |
| 8F-22 | 10.74             | 8.76            | 12.33         | 3.58   |                    |       |       |       |       |
| 8F-23 | 10.88             | 9.37            | 12.08         | 2.71   |                    |       |       |       |       |
| 8F-26 | 10.05             | 9.29            | 10.66         | 1.38   |                    |       |       |       |       |
| 8F-27 | 6.12              | 5.96            | 6.25          | .28    |                    |       |       |       |       |
| 8F-29 | 9.37              | 8.28            | 10.25         | 1.97   |                    |       |       |       |       |
| 8F-31 | 4.55              | 3.54            | 5.36          | 1.82   |                    |       |       |       |       |
| 8F-32 | 7.19              | 6.90            | 7.43          | .53    |                    |       |       |       |       |



**Table 13. Seal/Fluid Compatibility—Volume Change**

| MIL-H-6083 Fluids |        |        |        |        | MIL-H-46170 Fluids |        |        |        |        |
|-------------------|--------|--------|--------|--------|--------------------|--------|--------|--------|--------|
| Comp.             | H-6000 | H-6001 | H-6002 | H-6004 | HF-4               | HF-12  | HF-15  | MF-13  | MF-14  |
| 8F-1              | -9.56  | -8.72  | -12.39 | -8.97  | -10.93             | -11.37 | -11.15 | -11.00 | -11.10 |
| 8F-2              | 7.78   | 8.42   | 7.92   | 7.62   | 3.71               | 3.64   | 3.49   | 3.64   | 3.92   |
| 8F-3              | 8.14   | 7.90   | 10.36  | 8.73   | 4.52               | 4.62   | 3.50   | 4.08   | 4.68   |
| 8F-4              | 5.31   | 6.69   | 7.26   | 5.36   | .78                | -.06   | -.61   | .22    | 1.13   |
| 8F-5              | 3.03   | 4.06   | 4.33   | 2.97   | -2.26              | -2.04  | -3.00  | -2.28  | -1.55  |
| 8F-9              | 9.02   | 9.04   | 8.90   | 9.34   | 5.27               | 5.38   | 5.48   | 6.44   | 5.83   |
| 8F-10             | 63.06  | 65.25  | 65.45  | 65.17  | 20.71              | 21.61  | 20.11  | 20.52  | 22.65  |
| 8F-12             | 24.77  | 27.08  | 27.91  | 23.94  | 17.00              | 14.91  | 15.22  | 15.30  | 16.86  |
| 8F-13             | 7.67   | 8.93   | 8.94   | 7.29   | 3.16               | 3.90   | 1.77   | 2.14   | 3.86   |
| 8F-14             | 8.63   | 10.06  | 10.51  | 8.17   | 3.66               | 2.27   | 1.63   | 2.65   | 3.26   |
| 8F-16             | 9.46   | 9.26   | 9.62   | 8.26   | 3.94               | 3.70   | 3.49   | 3.52   | 4.52   |
| 8F-19             | 9.73   | 3.46   | 1.79   | 4.24   | 2.97               | 2.34   | 2.59   | 2.67   | 3.10   |
| 8F-22             | 7.21   | 4.87   | 2.36   | 5.40   | 3.01               | 2.36   | 1.96   | 2.17   | 2.38   |
| 8F-23             | 4.44   | 3.99   | 1.49   | 4.55   | 2.87               | 2.44   | 2.23   | 2.64   | 2.56   |
| 8F-26             | 14.50  | 15.64  | 15.21  | 13.44  | 11.90              | 9.11   | 8.70   | 10.02  | 11.36  |
| 8F-27             | 6.45   | 8.67   | 7.71   | 5.48   | 2.48               | .86    | .71    | 1.32   | 2.47   |
| 8F-29             | 10.82  | 12.35  | 12.61  | 10.10  | 6.03               | 3.32   | 2.91   | 3.50   | 4.64   |
| 8F-31             | 20.87  | 25.42  | 25.74  | 23.55  | 17.97              | 15.91  | 16.55  | 16.95  | 18.35  |
| 8F-32             | 14.63  | 16.11  | 16.50  | 14.87  | 11.30              | 11.45  | 10.80  | 11.76  | 11.76  |
| Avg.              | 11.89  | 12.55  | 12.22  | 11.55  | 5.69               | 4.97   | 4.55   | 5.07   | 5.83   |

|       | Row Avg. | H Fluid Avg. | HF/MF Avg. | Diff. | NBR-L (8F-31) Comparison |             |       |
|-------|----------|--------------|------------|-------|--------------------------|-------------|-------|
|       |          |              |            |       | Fluid                    | Mfr. R & CF |       |
|       |          |              |            |       |                          | 70°C        | 100°C |
| 8F-1  | -10.58   | -9.91        | -11.11     | 1.20  |                          |             |       |
| 8F-2  | 5.57     | 7.94         | 3.68       | 4.26  |                          |             |       |
| 8F-3  | 6.28     | 8.78         | 4.28       | 4.50  |                          |             |       |
| 8F-4  | 2.90     | 6.16         | .29        | 5.86  | H-6000                   | 25.0        | 20.0  |
| 8F-5  | .36      | 3.60         | -2.23      | 5.82  | H-6001                   | 26.0        | 25.4  |
| 8F-9  | 7.19     | 9.07         | 5.68       | 3.39  | H-6002                   | 26.5        | 25.7  |
| 8F-10 | 40.50    | 64.73        | 21.12      | 43.61 | H-6004                   | —           | 23.6  |
| 8F-12 | 20.33    | 25.93        | 15.86      | 10.07 | HF-4                     | 21.4        | 18.0  |
| 8F-13 | 5.30     | 8.21         | 2.97       | 5.24  | HF-12                    | 19.9        | 15.9  |
| 8F-14 | 5.65     | 9.34         | 2.69       | 6.65  | HF-15                    | 19.5        | 16.6  |
| 8F-16 | 6.20     | 9.15         | 3.83       | 5.32  | MF-13                    | 20.0        | 17.0  |
| 8F-19 | 3.65     | 4.81         | 2.73       | 2.07  | MF-14                    | 23.2        | 18.4  |
| 8F-22 | 3.52     | 4.96         | 2.38       | 2.58  |                          |             |       |
| 8F-23 | 3.02     | 3.62         | 2.55       | 1.07  |                          |             |       |
| 8F-26 | 12.21    | 14.70        | 10.22      | 4.48  |                          |             |       |
| 8F-27 | 4.02     | 7.08         | 1.57       | 5.51  |                          |             |       |
| 8F-29 | 7.36     | 11.47        | 4.08       | 7.39  |                          |             |       |
| 8F-31 | 20.15    | 23.90        | 17.15      | 6.75  |                          |             |       |
| 8F-32 | 13.24    | 15.53        | 11.41      | 4.11  |                          |             |       |


**Table 14. Retention of Properties—Mixed Fluid Immersion**

| Compound     | Tensile Ret.<br>% | Elong. Ret.<br>% | 200% Mod.<br>Ret. - % | Hard. Chge.<br>pts. | Vol. Chge.<br>% |
|--------------|-------------------|------------------|-----------------------|---------------------|-----------------|
| <b>8F-5</b>  |                   |                  |                       |                     |                 |
| H-6002       | 103               | 80               | *127                  | -1                  | 4.3             |
| HF-15        | 115               | 77               | *152                  | 6                   | -3.0            |
| Mixed        | 115               | 78               | *138                  | 1                   | -1.4            |
| <b>8F-12</b> |                   |                  |                       |                     |                 |
| H-6002       | 70                | 66               | *114                  | -14                 | 27.9            |
| HF-15        | 90                | 80               | 105                   | -10                 | 15.2            |
| Mixed        | 84                | 82               | 95                    | -8                  | 16.6            |

\* = 100% Mod.

|       | Tensile Product |       |       |
|-------|-----------------|-------|-------|
|       | H-6002          | HF-15 | Mixed |
| 8F-5  | 8.27            | 8.85  | 8.94  |
| 8F-12 | 4.62            | 7.20  | 6.86  |

# Tensile Product Averages MIL H-6083 vs. MIL H-46170

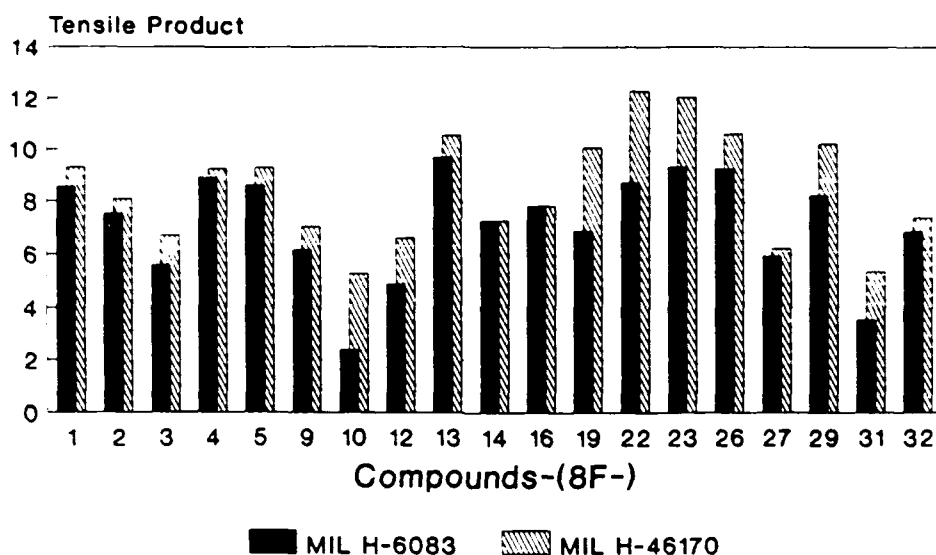

# Volume Change Averages MIL H-6083 vs. MIL H-46170


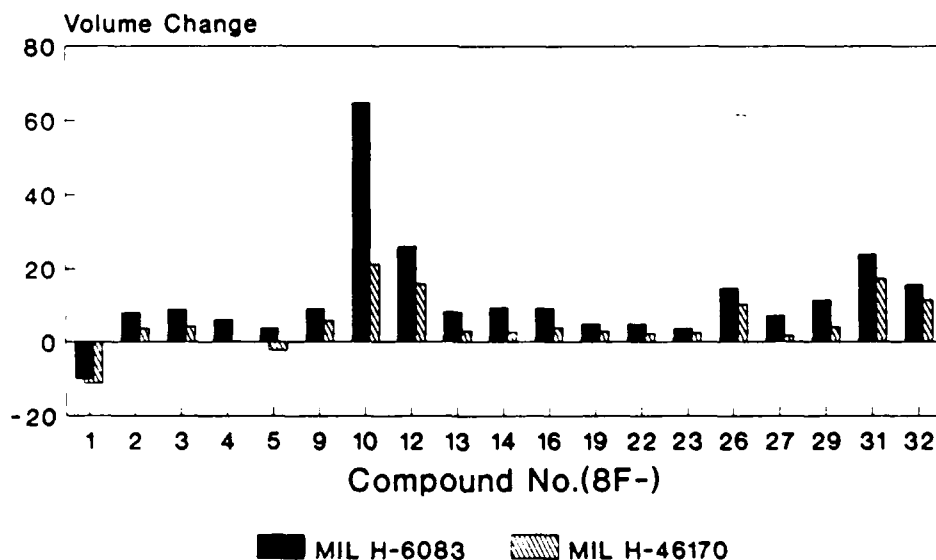


Figure 1. Tensile Product and Volume Change Averages, MIL-H-6083 vs. MIL-H-46170

## Tensile Product NBR-L vs. Group Average

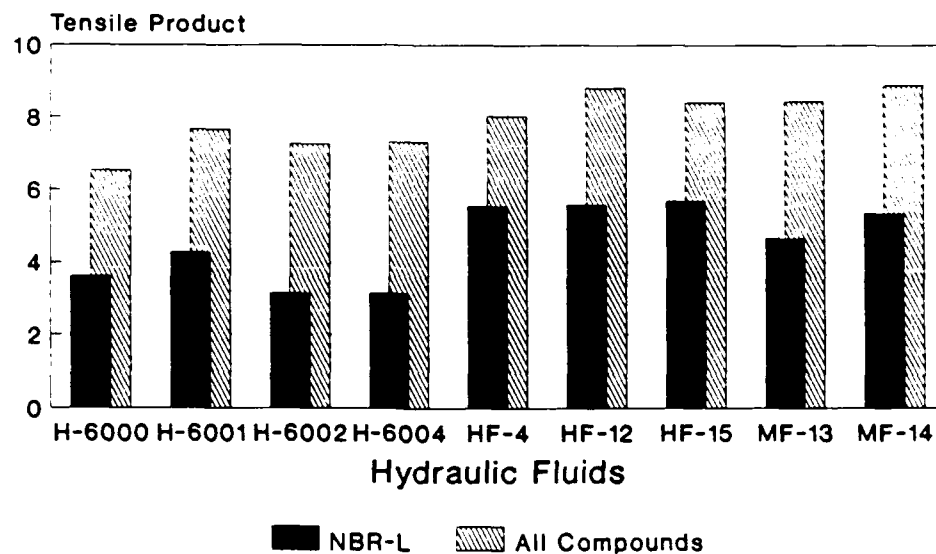

## Volume Change NBR-L vs. Group Average

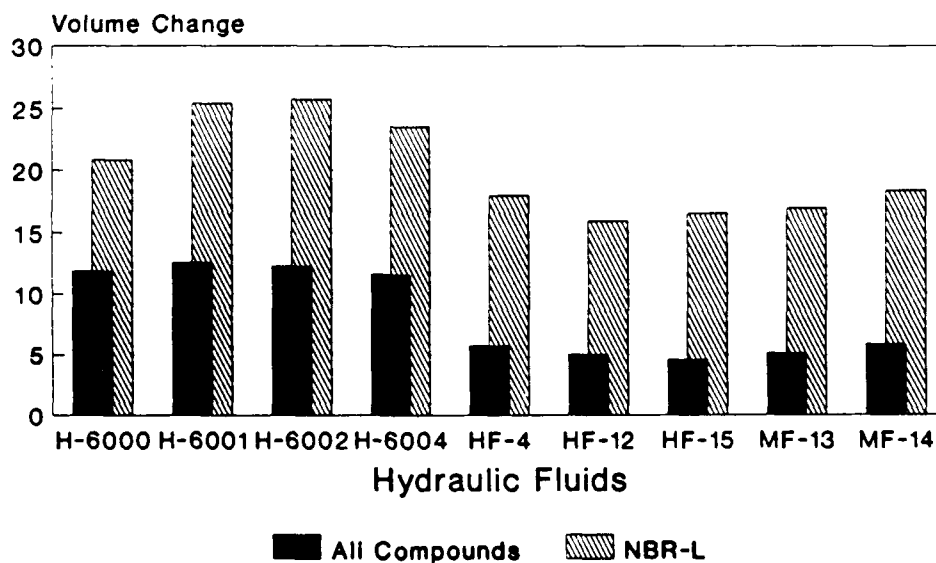


Figure 2. Tensile Product and Volume Change, NBR-L vs. Group Average

## DISTRIBUTION FOR REPORT NO. 2496

### DEPARTMENT OF DEFENSE

1 Director, Technical Information  
Defense Advanced Research Projects  
Agency  
1400 Wilson Blvd.  
Arlington, VA 22209

1 Director  
Defense Nuclear Agency  
ATTN: TITL  
Washington, DC 20305

2 Defense Technical Information Center  
Cameron Station  
ATTN: DTIC-FDAC  
Alexandria, VA 22304-6145

### DEPARTMENT OF THE ARMY

1 HQDA (DAMA-AOA-M)  
Washington, DC 20310

1 HQDA (DALO-TSM)  
Washington, DC 20310

1 HQDA (DAEN-RDL)  
Washington, DC 20314

1 DALO-TSE-W  
Washington, DC 20314

1 HQDA (DAEN-MPE-T)  
Washington, DC 20314

1 Commander  
US Army Missile Research & Development  
Command  
ATTN: AMSMI-PR  
Redstone Arsenal, AL 35809

1 Director  
Army Materials and Mechanics Research  
Center  
ATTN: AMXMR-RL Technical Library  
Watertown, MA 02172-0001

1 Commander  
Chemical Research R&D Center  
ATTN: SMCCR-SPS (Tech Library)  
Aberdeen Proving Ground, MD 21005

1 Commander  
US Army Aberdeen Proving Ground  
ATTN: STEAP-MT-U (GE Branch)  
Aberdeen Proving Ground, MD 21005

1 Director  
US Army Materiel Systems Analysis Agency  
ATTN: AMXSY-MP  
Aberdeen Proving Ground, MD 21005-5071

1 Director  
US Ballistics Research Laboratory  
ATTN: AMXBR-OD-ST (STINFO)  
Aberdeen Proving Ground, MD 21005-5066

1 Director  
US Army Engineer Waterways Experiment  
Station  
ATTN: Chief, Library Branch  
Technical Information Center  
Vicksburg, MS 39180

1 Commander  
US Army Armament Research &  
Development Command  
ATTN: SMCAR-TSS  
Dover, NJ 07801-5001

2 Commander  
US Army Troop Support Command  
ATTN: AMCPM-PWL  
4300 Goodfellow Blvd.  
St. Louis, MO 63120

2 Commandant  
US Army Quartermaster School and Center  
ATTN: ATSM-CDM  
Ft. Lee, VA 23801

- |  |  |
|--|--|
| <p>1 US Army Tank Automotive Command<br/>ATTN: DRSTA-TSL<br/>Warren, MI 48090</p> <p>1 US Army Laboratory Command<br/>ATTN: M. Levy SLCMT-MN<br/>Materials Technology Laboratory<br/>Watertown, MA 02172-0001</p> <p>1 US Army Laboratory Command<br/>ATTN: J. Wells SLCMT-MCZ<br/>Materials Technology Laboratory<br/>Watertown, MA 02172-0001</p> <p>1 Commander<br/>US Army Electronics Research &amp;<br/>Development Command<br/>ATTN: DELSD-L<br/>Fort Monmouth, NJ 07703-5301</p> <p>1 President<br/>US Army Aviation Test Board<br/>ATTN: STEBG-PO<br/>Fort Rucker, AL 36360</p> <p>1 US Army Aviation School Library<br/>PO Drawer O<br/>Fort Rucker, AL 36360</p> <p>1 HQ 193D Infantry Brigade (Panama)<br/>ATTN: AFZU-FE<br/>APO Miami 34004</p> <p>2 Special Forces Detachment, Europe<br/>ATTN: PBO<br/>APO New York 09050</p> <p>2 Engineer Representative<br/>USA Research &amp; Standardization Group<br/>(Europe)<br/>Box 65<br/>FPO 09510</p> <p>1 Commander<br/>Rock Island Arsenal<br/>ATTN: SARRI-LPL<br/>Rock Island, IL 61299-7300</p> | <p>1 Plastics Technical Evaluation Center<br/>ARRADCOM, Bldg 3401<br/>Dover, NJ 07801</p> <p>Commandant<br/>US Army Engineer School</p> <p>1 ATZA-CDD<br/>British Liaison Officer</p> <p>1 ATTN: ATSE-DAC-LB<br/>Fort Leonard Wood, MO 65473</p> <p>1 US Army AMCCOM<br/>ATTN: Joseph Menke<br/>1032 N. Thornwood<br/>Davenport, IA 52804</p> <p>1 Commander<br/>Headquarters, 39th Engineer Bn (Cbt)<br/>Fort Devens, MA 01433</p> <p>1 President<br/>US Army Airborne, Communications &amp;<br/>Electronics<br/>ATTN: STEBF-ABTD<br/>Fort Bragg, NC 28307</p> <p>1 President<br/>US Army Armor and Engineer Board<br/>ATTN: ATZK-AE-PD-E<br/>Fort Knox, KY 40121-5470</p> <p>1 Director<br/>ATTN: STSTO-TPP<br/>Tobyhanna Army Depot<br/>Tobyhanna, PA 18466-5097</p> <p>1 Commander and Director<br/>USA FESA<br/>ATTN: FESA-TS<br/>Fort Belvoir, VA 22060</p> <p>1 HQ, USAEUR &amp; Seventh Army<br/>Deputy Chief of Staff, Engineer<br/>ATTN: AEAEN-MT-P<br/>APO New York 09403</p> |
|--|--|

1 Director  
US Army TRADOC  
Systems Analysis Activity  
ATTN: ATAA-SL (Tech Lib)  
White Sands Missile Range, NM 88002

2 Commander  
Naval Facilities Engineering Command  
Department of the Navy  
ATTN: Code 032-B  
062  
200 Stovall Street  
Alexandria, VA 22332

#### **BELVOIR RD&E CENTER**

#### **Circulate**

1 Commander STRBE-Z  
Deputy Commander STRBE-ZD  
Technical Director STRBE-ZT  
Assoc Tech Dir (E&A) STRBE-ZTE  
Assoc Tech Dir (R&D) STRBE-ZTR  
Sergeant Major STRBE-ZM  
Advanced Systems Concept Dir STRBE-H  
Program Planning Div STRBE-HP  
Foreign Intelligence Div STRBE-HF  
Systems and Concepts Div STRBE-HC  
5 STRBE-V  
10 STRBE-VF  
10 STRBE-VU  
2 Tech Reports Office ASQNK-BVP-G  
3 Security Ofc (for liaison officers) STRBE-S  
2 Tech Lib STRBE-BT  
1 Public Affairs Office STRBE-I  
1 Office of Chief Counsel STRBE-L  
5 STRBE-FS

1 US Naval Oceanographic Office  
Navy Library/NSTL Station  
Bay St. Louis, MO 39522

Civil Engineering Laboratory  
Naval Construction Battalion Center  
1 Library (Code L08A)  
3 Code L-66  
Port Hueneme, CA 93043

1 Director  
Earth Physics Program  
Code 464  
Office of Naval Research  
Arlington, VA 22217

1 Naval Training Equipment Center  
ATTN: Technical Library  
Orlando, FL 32813

3 Naval Sea Systems Command  
ATTN: P. Schneider PMS377J1  
Washington, DC 20362-5101

1 Naval Air Development Center  
ATTN: V. S. Agarwala, Code 6062  
Warminster, PA 18974

3 David W. Taylor Naval Research Center  
ATTN: A. G. S. Morton  
Code 2813  
Annapolis, MD 21402

#### **DEPARTMENT OF THE NAVY**

1 Director  
Physics Program (421)  
Office of Naval Research  
Arlington, VA 22217

## **DEPARTMENT OF THE AIR FORCE**

- 1 HQ USAF/RDPT  
ATTN: Commander  
Washington, DC 20330
- 1 HQ USAF/PREEU  
Chief, Utilities Branch  
Washington, DC 20330
- 1 HQ Air Force Engineering & Services Ctr  
Technical Library FL7050  
Tyndall AFB, FL 32403
- 1 US Air Force  
Warner Robins Air Logistics Center  
WR-ALC/MMEM  
Warner-Robins AFB, GA 31098
- 1 Chief, Lubrications Branch  
Fuels & Lubrications Div  
ATTN: AFWAL/POSL  
Wright-Patterson AFB, OH 45433